

Effects of Spin Polarization on Electron Transport in Modulation Doped $\text{Cd}_{1-x}\text{Mn}_x\text{Te}/\text{Cd}_{1-y}\text{Mg}_y\text{Te:I}$ Heterostructures

T. Andrearczyk, J. Jaroszyński, G. Karczewski, J. Wróbel, T. Wojtowicz, and T. Dietl
Institute of Physics, Polish Academy of Sciences, al. Lotników 32/46, PL 02-668
Warszawa, Poland

E. Papis, E. Kamińska, and A. Piotrowska
Institute of Electron Technology, al. Lotników 32/46, PL 02-668 Warszawa, Poland

Abstract

We examine and identify magnetoresistance mechanisms in 2D system containing a sizable concentration of magnetic ions. We argue that some of these mechanisms can serve as a tool to measure spin polarization. Lack of spin degeneracy and enhanced localization make it possible to detect an additional QHE plateau associated with extended states floating-up in vanishing magnetic field.

In diluted magnetic semiconductors (DMS), owing to the strong s-d exchange between the effective mass carriers and the localized Mn spins, a high degree of spin-polarization of the carrier liquid can be achieved in moderately strong magnetic fields [1]. This offers a tool to find out how properties of quantum structures evolve as a function of spin polarization. Our work extends previous transport studies of II-VI DMS low-dimensional systems [2, 3, 4, 5, 6, 7] in two major directions. First, one of the challenging problems that face spintronics [8] is how to read the local spin configuration. We have combine millikelvin studies of low-field magnetoconductance with theoretical calculations in order to single out possible effects of spin-polarization on electron transport in high electron mobility modulation-doped heterostructures of $\text{Cd}_{1-x}\text{Mn}_x\text{Te}/\text{Cd}_{1-y}\text{Mg}_y\text{Te:I}$. Based on our results, we argue that the temperature dependence of conductivity can serve as a tool to detect and quantify the degree of carrier polarization generated, for instance, by spin injection.

Second, it has been already demonstrated that the large spin-splitting in $\text{Cd}_{1-x}\text{Mn}_x\text{Te}$ makes it possible to test quantitatively scaling theory of the quantum Hall effect (QHE) over a wide range of the filling factors ν [7]. Importantly, such a system offers also a novel environment to examine the transition between electron liquid and quantum Hall states. Scaling theory of localization predicts that only localized states exist at zero magnetic field in two dimensional (2D) systems. Thus, according to Khmelnitskii [9] and Laughlin [10], extended states associated with Landau levels should float up and cross the Fermi energy when $B \rightarrow 0$. Hence, the resulting global phase diagram of the QHE [11] allows only for a direct transition between the insulating phase and the QHE liquid state with the filling factor $\nu = 1$. If the spin degeneracy is not removed, the diagram predicts the transition involving the $\nu = 2$ QHE state. However, a number of recent experiments call into question this picture. In particular, a zero-field metallic state is observed [12], the floating scenario is questioned [13], and transition from the insulating phase into QHE states with $\nu \geq 3$

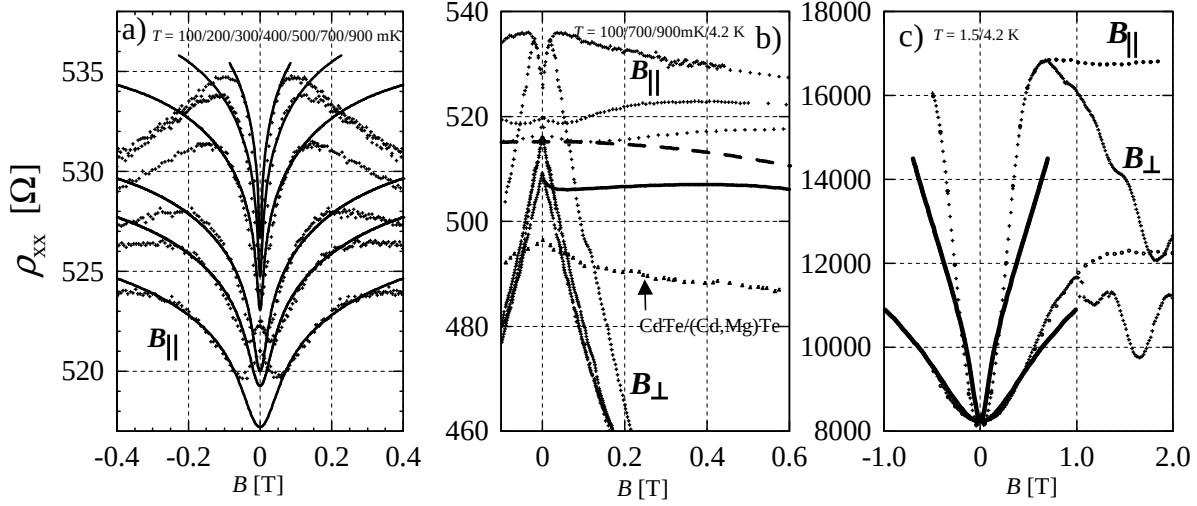


Figure 1: Low-field magnetoresistance (MR) in heterostructures with electron density and net Mn concentration $n_s = 5.9 \times 10^{11} \text{ cm}^{-2}$, $x = 0.005$, respectively, in parallel (a) and perpendicular (b) configurations. (c) MR for $n_s = 1.35 \times 10^{11} \text{ cm}^{-2}$; $x = 0.05$. MR for the nonmagnetic CdTe with similar density and mobility is also shown in (b). Thick solid lines are calculated taking effects of disorder on electron-electron interactions into account [18, 19, 20, 21]. The data demonstrate that current theory explains the positive MR but fails to describe an additional Mn-induced negative MR in the perpendicular configuration.

are reported [14, 15, 16]. The latter, however, are interpreted also as a cross-over, not the quantum phase transition, occurring between the QHE and weak localization regimes, each characterized by rather different conductivities at non-zero temperatures [17]. We have carried out a detail study of the boundary between the electron and QHE liquids with the hope that a large ratio of the spin and cyclotron splittings will result in a better resolution. Indeed, we detect an additional plateau $\sigma_{xy} \approx e^2/h$ in a sample with the lowest electron concentration, which we assign to the floating $\nu = 1$ Landau level.

The Mn ions were introduced to the quantum wells (QW) either digitally or uniformly, the mean Mn content varying between $x = 0.005$ and $x = 0.05$. In these structures the electron density varies between $n_s = 1.35 - 5.9 \times 10^{11} \text{ cm}^{-2}$, and electron mobility up to $60\,000 \text{ cm}^2/\text{Vs}$ is observed. As shown in Fig. 1, the presence of Mn leads to giant spin-related positive as well as to negative MR, the latter of an orbital origin as it is observed only for the magnetic field perpendicular to the QW plane. The quantitative analysis of the data is based on theory of quantum corrections to conductivity σ of disordered systems [18, 19, 20, 21], using codes and procedures developed previously [3, 22, 23]. As shown, the model does not account for the negative MR, which suggests the presence of a new Mn-induced phenomenon. By contrast, in agreement with the earlier studies [3, 4, 22], we find that the positive MR stems from the effect of giant spin-splitting upon interference of electron-electron interaction amplitudes in disordered systems. The calculated MR agrees well with the experimental data, particularly for the sample with $n_s = 5.9 \times 10^{11} \text{ cm}^{-2}$. In the case of the sample with the lower density $n_s = 1.35 \times 10^{11} \text{ cm}^{-2}$, a discrepancy between the observed and calculated MR appears at low temperature, presumably because of the

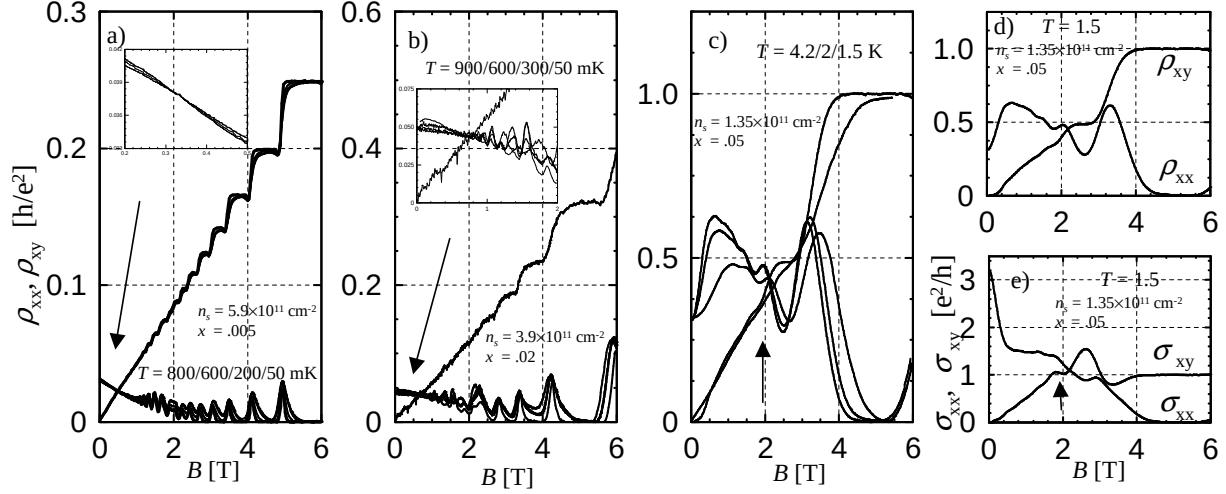


Figure 2: Longitudinal and Hall resistivities in devices with (a) $n_s = 5.9 \times 10^{11} \text{ cm}^{-2}$, $x = 0.005$, (b) $n_s = 3.9 \times 10^{11} \text{ cm}^{-2}$, $x = 0.02$ and (c) $n_s = 1.35 \times 10^{11} \text{ cm}^{-2}$, $x = 0.05$. Insets to (a) and (b) show the the field range corresponding to the transition between the spin-polarized liquid and quantum Hall effect regimes. (d)(e) transport coefficients in the device with $n_s = 1.35 \times 10^{11} \text{ cm}^{-2}$, $x = 0.05$ at 1.5 K. Arrow indicates an additional plateau of σ_{xy} , assigned to the floating Landau level.

proximity to the strongly localized regime as well as the effect of the redistribution of the carriers between the spin subbands, a MR mechanism [24] neglected in our computations.

Our results imply that quantum localization effects in 2D systems make σ to be sensitive to spin polarization not only in low mobility materials studied previously [3, 4, 6, 22] but also in the case of 2D systems containing high mobility carriers. Actually, the value of σ depends on the ratio of temperature to the energy distance between quasi Fermi levels for the two spin subbands, and not on σ itself. This means, in particular, that temperature dependence of σ may serve to determine quantitatively the efficiency of spin injection into a 2D electron liquid.

Figure 2 summarizes results of MR and Hall effect measurements for three samples with increasing disorder and Mn concentrations in the range of the magnetic field corresponding to the transition between the classically weak and strong magnetic fields, $\rho_{xx} \approx \rho_{xy}$. At first glance, the results look similar to those reported for 2D nonmagnetic systems [14, 15, 16]. In particular, at $\rho_{xx} = \rho_{xy}$, ρ_{xx} becomes virtually temperature independent. Furthermore, a cross-over from the weakly localized regime into $\nu = 11, 6, 2$ QHE states is observed for heterostructures with $n_s = 5.9, 3.9$, and $1.35 \times 10^{11} \text{ cm}^{-2}$, respectively.

However, in the device with density $n_s = 1.35 \times 10^{11} \text{ cm}^{-2}$ the presence of the Shubnikov-de Haas oscillations in the magnetic field lower than the cross-over point are clearly seen. Moreover, an additional $\sigma_{xy} \approx e^2/h$ plateau is observed in this field range, as shown in Fig. 2(e). We assign this plateau to the floating lowest Landau level, as theoretically predicted [9, 10] but hardly observed so far. Most probably, the large spin-splitting and the enhanced localization have made our search successful. Interestingly, recent theoretical [25] and experimental results [13] indicate that, at least in the case of the spin-polarized electron liquid, the extended states float-up in vanishing magnetic fields.

In conclusion, the spin polarization affects interference of electron-electron interaction amplitudes, which leads to a large reduction of conductivity even for a small magnitude of spin polarization. Under such conditions, a transition between spin polarized carrier liquid and QHE states has been detected. This observation corroborates the scenario of floating up Landau levels. The presence of Mn results also in a large negative orbital magnetoresistance, whose origin is unknown at present.

This work was supported by Foundation for Polish Science and KBN grant No. 2-P03B-02417.

References

- [1] For a review on DMS, see, *e.g.*, T. Dietl, in Handbook on Semiconductors, eds. T.S. Moss, (North-Holland, Amsterdam, 1994) vol. 3b, p. 1251.
- [2] G. Grabecki *et al.* Semicond. Sci. Technol. 8 (1993) S95.
- [3] J. Jaroszyński *et al.*, Phys. Rev. Lett. 75 (1995) 3170.
- [4] I. P. Smorchkova *et al.*, Phys. Rev. Lett. 78 (1997) 3571 .
- [5] J. Jaroszyński *et al.* Phys. Rev. Lett. 80 (1998) 5635.
- [6] I.P. Smorchkova *et al.*, Phys. Rev. B 58 (1998) R4238.
- [7] J. Jaroszyński *et al.*, Physica E 6 (2000) 790.
- [8] See, *e.g.*, G.A. Prinz, Science 282 (1998) 1660.
- [9] D.E. Khmiel'nitskii, (JETP Lett. 38 (1984) 552.
- [10] R.B. Laughlin, Phys. Rev. Lett. 52 (1984) 2304.
- [11] S. Kivelson, D.-H. Lee and S.-C. Zhang, Phys. Rev. B 46 (1992) 2223.
- [12] See, E. Abrahams, S.V. Kravchenko and M.P. Sarachik, Rev. Mod. Phys. 73 (2001) 251, and references therein.
- [13] S.V. Kravchenko *et al.*, this Conference.
- [14] S.-H. Song *et al.*, Phys. Rev. Lett. 78 (1997) 2200.
- [15] C.H. Lee, Y.H. Chang, Y.W. Suen, H.H. Lin, Phys. Rev. B 58 (1998) 10629.
- [16] M. Hilke *et al.*, Phys. Rev. B 62 (2000) 6940.
- [17] B. Huckenstein, Phys. Rev. Lett. 84 (2000) 3142.
- [18] B.L. Altshuler and A.G. Aronov, in *Electron-Electron Interaction in Disordered Systems*, edited by A.L. Efros and M. Pollak (North-Holland, Amsterdam, 1985), p. 1.
- [19] H. Fukuyama, *ibid.*, p. 155.
- [20] P.A. Lee and T.V. Ramakrishnan, Rev. Mod. Phys. 57 (1985) 287.
- [21] M.A. Paalanen, D.C. Tsui and J.C.M. Hwang, Phys. Rev. Lett. 51 (1983) 2226 .
- [22] M. Sawicki *et al.*, Phys. Rev. Lett. 56 (1986) 508.
- [23] G. Brunthaler *et al.*, Semicond. Sci. Techn. 11 (1996) 1624.
- [24] H. Fukuyama and K. Yoshida, J. Phys. Soc. Jpn. 46 (1979) 1522.
- [25] Th. Koschny, H. Potempa, and L. Schweitzer, Phys. Rev. Lett. 86 (2001) 3863.